

Yamada Conference LVI, the Fourth International Symposium on Crystalline Organic Metals,
Superconductors and Ferromagnets

ISCOM 2001 - Abstract Number S67

1

Thermal Conductivity in Vortex State of Nodal Superconductors

H. Won^a *, and K. Maki^b ^c

^aDepartment of Physics, Hallym University, Chunchon, 200-702, South Korea

^bDepartment of Physics and Astronomy, University of Southern California, Los Angeles CA 90089-0484, USA

^cMax-Planck Institut für Physik Komplexer Systeme, Nöthnitzer Str.38, D-01187, Dresden, Germany

How to determine the symmetry of the superconducting order parameter is one of the important issues in novel superconductors, which include charge conjugated organic superconductors. We have proposed that the angular dependence of the thermal conductivity in a planar magnetic field provides a new window to look at the symmetry of the order parameter. After a brief summary of the quasiclassical approach we describe how the symmetry of the superconducting order parameter in Sr_2RuO_4 , CeCoIn_5 and $\kappa\text{-(ET)}_2\text{Cu(NCS)}_2$ is determined. Also in some of experiments the phononic thermal conductivity plays the crucial role.

Keywords: Unconventional superconductors, Thermal conductivity, Vortex state

1. Introduction

Since the discovery of the first organic superconductor in $(\text{TMTSF})_2\text{PF}_6$ (or Bechgaard salts) [1], the symmetry in superconducting order parameter has been one of the important issues [2,3]. Indeed the symmetry of the superconducting order parameter becomes one of the central issues after the establishment of d -wave symmetry in both hole and electron doped high T_c superconductors [4,5,6,7]. Most likely the superconductivity in $(\text{TMTSF})_2\text{X}$ with $\text{X} = \text{ClO}_4$, PF_6 , etc. is of p -wave [8]. In particular, a flat Knight shift seen in a recent NMR experiment [9] is consistent with this picture. The remaining question is whether the p -wave superconductor belongs to 1D representation [3] or 2D representation [8]. After

a long controversy [10], d -wave superconductivity is emerging in $\kappa\text{-(ET)}_2$ salts [11,12,13,14,15]. Here now the question is whether the symmetry is of d_{xy} -wave as suggested by the theoretical works [16,17,18] or $d_{x^2-y^2}$ -wave as the recent STM study suggests [15]. We shall give a somewhat surprising answer on this based on the recent angular dependent thermal conductivity data of $\kappa\text{-(ET)}_2\text{Cu(NCS)}_2$ by Izawa et al [19]. The quasiparticle spectrum of all these new superconductors is well described by the BCS theory for nodal (or unconventional) superconductors [6,7,20]. In particular, there are nodal excitations (i.e. the quasiparticles which inhabit in the vicinity of the nodal lines) which persist to low temperatures (i.e. $T \ll \Delta$ where Δ is the superconducting order parameter). In the vortex state the quasiparticle spectrum is modified due to the supercurrent circling around individual vortices. In order to describe the quasiparticle spectrum in the vortex state, Volovik [21] has introduced a very simple method to evaluate the effect of the supercurrent within the quasiclassical approximation. In particular, he has shown that the specific heat in the vortex state in nodal superconductors

*HW acknowledges the support by the Hallum Academy of Science, Hallym University. We thank Y. Matsuda and K. Izawa for keeping us informed about ongoing experiments on $\kappa\text{-(ET)}_2\text{Cu(NCS)}_2$ and useful discussions. Also discussions with M. A. Tanatar and Y. Maeno on the c -axis thermal conductivity in Sr_2RuO_4 which initiate our study of the phononic thermal conductivity are gratefully acknowledged. We thank also M. A. Tanatar for providing us the digitalized version of the experimental data from Ref.[47], which we used in Fig. 2 and Fig.3.

is proportional to $\sqrt{H}$ for $H/H_{c2} \ll 1$ where H is the magnetic field strength. This $\sqrt{H}$ dependence has been seen in YBCO [22,23,24], LSCO [25], κ -(ET)₂ salts [12] and Sr₂RuO₄ [26,27]. We shall show later that in the presence of impurity the above dependence may change as [28]

$$\frac{C_s}{\gamma_N T} = \frac{N(0)}{N_0} \left\{ 1 + \frac{\Delta}{\pi \Gamma} \langle x^2 \rangle \right\} \\ = \frac{N(0)}{N_0} \left\{ 1 + \frac{3\tilde{v}^2(eH)}{16\pi\Gamma\Delta} \left[\ln \left(\sqrt{\frac{3}{2(eH)}} \frac{\Delta}{\tilde{v}} \right) - \frac{1}{27} \right] \right\} \quad (1)$$

for Sr₂RuO₄ in $H//$ a-b. Similarly for $d+s$ -wave in $H//$ a-b,

$$\frac{C_s}{\gamma_N T} = \frac{N(0)}{N_0} \left\{ 1 + \frac{\tilde{v}^2(eH)}{8\pi\Gamma\Delta} \left[\left(1 - \frac{1}{2} r \cos(2\theta) \right) \times \right. \right. \\ \left. \left. \ln \left(\frac{\Delta}{\tilde{v}\sqrt{eH}} \right) - \frac{1}{16} \left(1 - \frac{1}{2} (1 - 2r^2) \cos(4\theta) \right) \right] \right\} \quad (2)$$

Here $N(0)$ is the residual density of states in the presence of the impurity scattering and N_0 is the one for the normal state. Also γ_N is the Sommerfeld coefficient, $\tilde{v} = \sqrt{v_a v_c}$ and v_a and v_c are the Fermi velocities in the a-b plane and parallel to the c-axis, respectively. For $d+s$ -wave we took $\Delta(\mathbf{k}) \propto \cos(2\phi) - r$. θ is the angle $\mathbf{H}$ makes from the a axis. Here $x = \mathbf{v} \cdot \mathbf{q}/\Delta$ and $\mathbf{v} \cdot \mathbf{q}$ is called the Doppler shift, where $\mathbf{v}$ is the Fermi velocity and $2\mathbf{q}$ is the pair momentum and $\langle \dots \rangle$ means space average over the vortex lattice and $\mathbf{v}$ average over the nodal lines. Some of these details are given in [29]. In the above derivation, we have assumed that the system is in the clean limit ($\epsilon, T \ll \sqrt{\Gamma\Delta}$) while Volovik's result applies for the superclean limit ($\sqrt{\Gamma\Delta} \ll \epsilon, T$). Here $\epsilon = \frac{1}{2}\tilde{v}\sqrt{eH}$ is the characteristic magnetic energy. Also when we put $r = 0$ in Eq.(2), we obtain the usual expression for d -wave superconductors. The specific heat in the clean limit in LSCO in $\mathbf{H} \parallel c$ has been reported recently[30]. The quasiclassical approximation is extended to calculate the thermal conductivity in the vortex state [28,31,32,33,34]. Indeed we can now describe the angular dependent thermal conductivity observed in single crystals of YBCO [35,36,37,38] consistently if we assume that the system is in the superclean limit and $T \gg \epsilon$ [34]. In the following we shall first review the theory

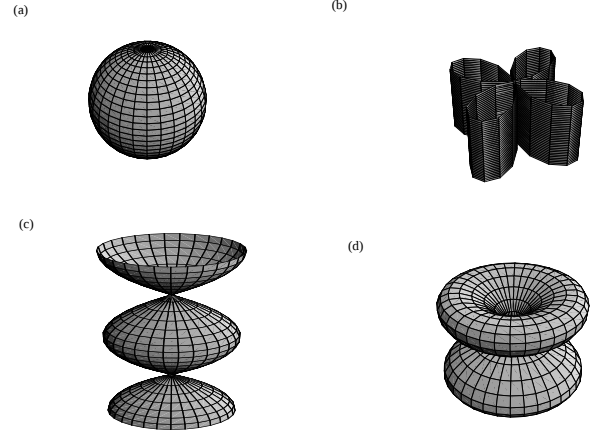


Figure 1. $|\Delta(\mathbf{k})|$'s for s -wave and some of unconventional superconductors are shown: (a) s -wave superconductor, $\Delta(\mathbf{k}) = \Delta$ (b) $d_{x^2-y^2}$ -state, $\Delta(\mathbf{k}) \sim \cos(2\phi)$ (c) 2D f -wave, $\Delta(\mathbf{k}) \sim \cos(ck_z)e^{\pm i\phi}$ (d) E_{2u} -state, $\Delta(\mathbf{k}) \sim \cos\theta \sin^2\theta e^{\pm i\phi}$

limiting ourselves to the clean limit ($\epsilon \ll \sqrt{\Gamma\Delta}$). As to the result for the superclean limit readers may consult [27,34,39]. Also we consider the phononic thermal conductivity both in Sr₂RuO₄ and in κ -(ET)₂ salts. The c-axis thermal conductivity in Sr₂RuO₄ [40] appears to be described in terms of the phononic thermal conductivity [41]. As to κ -(ET)₂Cu(NCS)₂ it appears the phononic thermal conductivity dominates for $T > 0.5\text{K}$ [19,41]. For $T < 0.47\text{K}$ there appears a clear sign of the electronic contribution. From the angle dependence of the thermal conductivity, we can deduce $d+s$ -wave ($\Delta(\mathbf{k}) \propto \cos(2\phi) - 0.067$) for κ -(ET)₂Cu(NCS)₂. In Fig.1 we show $|\Delta(\mathbf{k})|$ for superconductors a) s -wave, (b) d -wave as in HTSC, CeCoIn₅[42], κ -(ET)₂ salts[19], (c) 2D f -wave as in Sr₂RuO₄[26,27] and (d) f -wave as in UPt₃ [43,44,45].

2. Thermal conductivity in the vortex state.

In the following we limit ourselves to nodal superconductors; 2D f -wave with $\Delta(\mathbf{k}) \propto \cos(ck_z)e^{\pm i\phi}$ as in Sr_2RuO_4 and $d + s$ -wave with $\Delta(\mathbf{k}) \propto \cos(2\phi) - r$ as in $\kappa\text{-(ET)}_2\text{Cu(NCS)}_2$. Also we limit ourselves to the clean limit (i.e. $\sqrt{\Delta\Gamma} \gg \epsilon = \tilde{v}\sqrt{eH}$, where $\tilde{v} = \sqrt{v_a v_b}$) [27]. Then the thermal conductivity for $T \ll \Delta$ and in a planar magnetic field is given by

$$\frac{\kappa_{xx}}{\kappa_0} = 1 + \frac{\tilde{v}^2(eH)}{4\pi\Gamma\Delta} \ln(4\sqrt{\frac{2\Delta}{\pi\Gamma}}) \left(\ln\left(\frac{\Delta}{\tilde{v}}\sqrt{\frac{2}{3eH}}\right) - \frac{1}{72} \right) \quad (3)$$

for 2D f -wave.

$$\begin{aligned} \frac{\kappa_{xx}}{\kappa_0} = & 1 + \frac{\tilde{v}^2(eH)}{6\pi\Gamma} \ln(4\sqrt{\frac{2\Delta}{\pi\Gamma}}) \left(\left(1 - \frac{1}{2}r \cos(4\theta)\right) \times \right. \\ & \left. \ln\frac{2\Delta}{\tilde{v}\sqrt{eH}} - \frac{1}{16} \left(1 - \frac{1}{2}(1 - 2r^2) \cos(2\theta)\right) \right) \end{aligned} \quad (4)$$

for $d + s$ -wave.

Similarly the Hall thermal conductivity is given by

$$\frac{\kappa_{xy}}{\kappa_0} = -\frac{\tilde{v}^2(eH)}{24\pi\Gamma\Delta} \sin(2\theta) \ln(2\sqrt{\frac{2\Delta}{\pi\Gamma}}) \ln\left(\frac{\Delta}{\tilde{v}}\sqrt{\frac{2}{3eH}}\right) \quad (5)$$

for 2D f -wave, and

$$\begin{aligned} \frac{\kappa_{xy}}{\kappa_0} = & -\frac{\tilde{v}^2(eH)}{16\pi\Gamma\Delta} (1 - r^2) \sin(2\theta) \ln(4\sqrt{\frac{2\Delta}{\pi\Gamma}}) \times \\ & \ln\left(\frac{\Delta}{\tilde{v}\sqrt{eH}}\right) \end{aligned} \quad (6)$$

for $d + s$ -wave. Here κ_0 is the thermal conductivity in the absence of the magnetic field.

3. Phononic thermal conductivity

So far we have considered only the electronic thermal conductivity. In general, the thermal conductivity is written as $\kappa = \kappa^{el} + \kappa^g$, where the second term is due to phonons. The importance of κ^g in high T_c cuprate superconductors, YBCO and Bi2212 have been well-documented [46]. In low temperatures (for $T < 5\text{K}$) $\kappa^g \sim T^3$ in single crystals of YBCO and Bi2212 [46]. In high quality crystals phonons are mostly scattered by crystalline defects and crystal boundaries. In the vortex state in nodal superconductors the quasiparticles provide another scattering center. When the

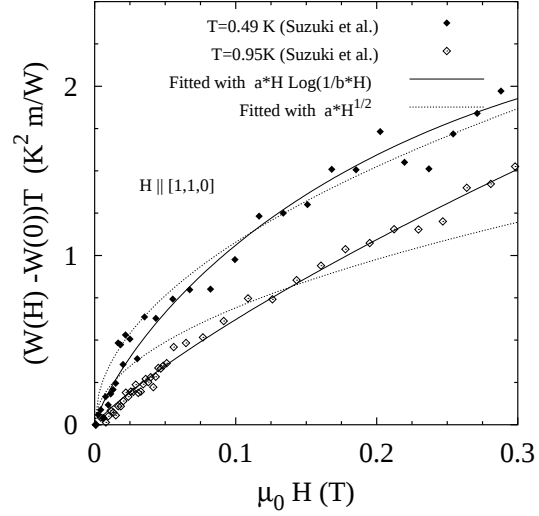


Figure 2. The field dependence of the thermal resistance in the magnetic field along $[110]$ direction within the plane Ref.[47] is compared with the fitted $aH * \log(1/b * H)$ and $\sqrt{H}$.

thermal phonons are ballistic, the phonon scattering due to the quasiparticles is proportional to $[N(0, \theta)]^2$ at low temperatures [41]. Here $N(0, \theta)$ is the residual density of states in the presence of a magnetic field and θ refers to the field orientation. Therefore the c axis phononic thermal conductivity κ^g in Sr_2RuO_4 is a planar magnetic field is written

$$\frac{\kappa^g}{\kappa_0^g} = \left[1 + \frac{T}{T_0} \left(1 + \frac{3\tilde{v}^2(eH)}{8\pi\Gamma\Delta} \ln\left(\frac{T}{c\sqrt{eH}}\right) \right) \right]^{-1} \quad (7)$$

for 2D f -wave, and

$$\frac{\kappa^g}{\kappa_0^g} = \left[1 + \frac{T}{T_0} \left(1 + \frac{\tilde{v}^2(eH)}{4\pi\Gamma\Delta} \left(1 - \frac{r}{2} \cos(2\theta) \right) \ln\left(\frac{T}{c\sqrt{eH}}\right) \right) \right]^{-1} \quad (8)$$

for $d + s$ -wave, respectively. Here T_0 is a constant of the dimension of the energy, and c is the phonon velocity. It is noteworthy that Eq.(8) does not contain the fourfold term.

When the phononic thermal conductivity dominates as in Sr_2RuO_4 [47], it is more convenient

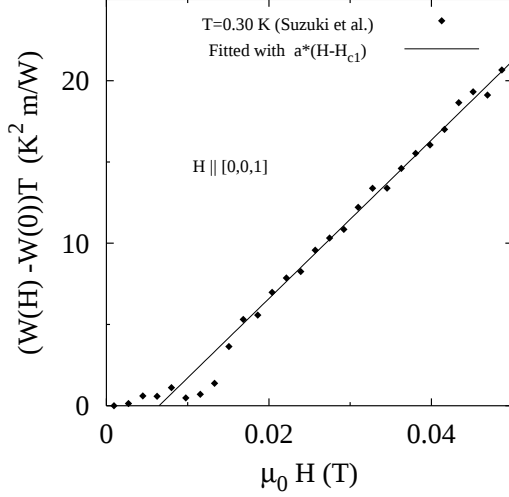


Figure 3. The interplane field dependence of the thermal resistance Ref.[47] is compared with $a * (H - H_{c1})$.

to analyze the thermal resistance $W = (\kappa^g)^{-1}$

$$\frac{W(H)}{W(0)} - 1 = \frac{T}{T + T_0} \frac{3\tilde{v}^2(eH)}{8\pi\Gamma\Delta} \ln\left(\frac{T}{c\sqrt{eH}}\right) \quad (9)$$

for 2D f -wave. We believe $aH \ln(1/bH)$ dependence is more consistent with the experiment for $H \parallel [100]$, which indicates the crystal of Sr_2RuO_4 is in the clean limit. This is readily seen from Fig.2. Also in the clean limit the specific heat behaves similarly [47]. On the other hand for $\mathbf{H} \parallel [001]$, it appears that the superclean limit appears, ie. linear in H as shown in Fig. 3.

More recently the b -axis thermal conductivity of $\kappa\text{-(ET)}_2\text{Cu(NCS)}_2$ in a planar magnetic field is reported [19]. First of all for $T > 1$ K the thermal conductivity decreases with increasing H indicating the phonon dominance. more surprising is an appreciable twofold term ($\sim \cos(2\theta)$) in the thermal conductivity. This suggests naturally $d + s$ -wave model. Indeed we obtain $\Delta(\mathbf{k}) \sim \cos(2\phi) - 0.067$ as already mentioned earlier. As the temperature is lowered through $T = 0.47$ K, there appears a positive fourfold term. Clearly

this is the signature of the electronic thermal conductivity. Further the magnitude of the fourfold term is consistent with Eq.(4). Therefore we conclude the order parameter in $\kappa\text{-(ET)}_2\text{Cu(NCS)}_2$ is of $d + s$ -wave with $\Delta(\mathbf{k}) \sim \cos(2\phi) - 0.067$. In other words the nodal lines run 43.08° from the b -axis rather than 45° . Since $\kappa\text{-(ET)}_2$ salts do not have the tetragonal symmetry, the admixture of s -wave component is allowed. This is somewhat similar to YBCO, where the tetragonal symmetry is broken due to the orthorhombic distortion[48]. This $d_{x^2-y^2}$ -wave is totally unexpected theoretically [16,17,18,19]. There is a well-known parallel between high T_c cuprates and $\kappa\text{-(ET)}_2$ salts. However, the present result tells there is a subtle and delicate difference between these two systems and a more careful study of the pairing interaction is necessary. This makes the physics in organic superconductors all the more interesting.

4. Concluding Remarks

The gap symmetry is the central issue of new superconductors. We have shown the angular dependent thermal conductivity in the vortex state provides a new window to look this question. In this way we have succeeded in identifying the gap symmetry of Sr_2RuO_4 , CeCoIn_5 [42,49] and $\kappa\text{-(ET)}_2\text{Cu(NCS)}_2$ [19]. We expect this method will be very useful to identify the gap symmetry of $\beta\text{-(ET)}_2$ salts, $\lambda\text{-(ET)}_2$ salts and other organic superconductors and to clarify existing controversy. Also the success of this method testifies the soundness of both the BCS theory of nodal superconductors and the Volovik's semiclassical approach to handle the vortex state in nodal superconductors.

REFERENCES

1. D. Jérôme, A. Mazaud, M. Ribault, K. Bechgaard, J. Phys. Lett. 41, L95 (1980).
2. M. Takigawa, H. Yasuoka, G. Saito, J. Phys. Soc. Jpn. 56, 873 (1987).
3. Y. Hasegawa, H. Fukuyama, J. Phys. Soc. Jpn. 56, 877 (1987).
4. J. van Harlingen, Rev. Mod. Phys. 67, 515 (1995).
5. C. C. Tsuei and J. R. Kirtley, Rev. Mod. Phys. 72, 969 (2000).

6. K. Maki and H. Won, J. Phys. I (Paris) 6, 2317 (1996).
7. K. Maki, H. Won, M. Kohmoto, J. Shiraishi, Y. Morita, G. F. Wang, Physica C 317-318, 353 (1999).
8. K. Maki, E. Puchkaryov and H. Won, Synth. Metals 703, 1933 (1999).
9. I. J. Lee, S. E. Brown, W. G. Clark, M. J. Strouse, M. J. Naughton, W. Kang, and P. M. Chaikin, Phys. Rev. Lett. 88, 017004 (2001).
10. M. Lang, Superconductivity Review 2, 1 (1996).
11. H. Mayaffre, P. Wzietek, D. Jérôme, C. Lenoir, and P. Batail, Phys. Rev. Lett. 75, 4122 (1995).
12. Y. Nakagawa and K. Kanoda, Phys. Rev. B 55, R8670 (1997).
13. A. Carrington, I. J. Bonalde, R. Prozorov, and R. W. Giannetta, A. M. Kini, J. Schlueter, H. H. Wang, U. Geiser, and J. M. Williams, Phys. Rev. Lett. 83, 4172 (1999).
14. M. Pinterić, S. Tomić, M. Prester, D. Drobac, and O. Milat, K. Maki, D. Schweitzer, I. Heinen and W. Strunz, Phys. Rev. B 61, 7033 (2000).
15. T. Arai, K. Ichimura, and K. Nomura, S. Takasaki, J. Yamada, S. Nakatsuji, and H. Anzai, Phys. Rev. B 63, 104518 (2001).
16. G. Visentini, A. Painelli, A. Girlando, and A. Fortunelli, Europhys. Lett. 42 467 (1998).
17. J. Schmalian, Phys. Rev. Lett. 81, 4232 (1998).
18. R. Louati, S. Charfi-Kaddour, A. Ben Ali, R. Benaceur, and M. Heritier, Phys. Rev. B 62 5957 (2000).
19. K. Izawa, H. Yamaguchi, T. Sasaki, and Y. Matsuda Phys. Rev. Lett. 88, 027002 (2002).
20. H. Won and K. Maki, Phys. Rev. B 49, 1397 (1994).
21. G. E. Volovik, JETP Lett. 58, 469 (1993).
22. K. A. Moler, D. J. Baar, J. S. Urbach, Ruixing Liang, W. N. Hardy, and A. Kapitulnik, Phys. Rev. Lett. 73, 2744 (1994).
23. K. A. Moler, David L. Sisson, Jeffrey S. Urbach, Malcolm R. Beasley, Aharon Kapitulnik, David J. Baar, Ruixing Liang, and Walter N. Hardy Phys. Rev. B 55, 3954 (1997).
24. B. Revas, J. Y. Genoud, A. Junod, K. Neumaier, A. Erb, and E. Walker, Phys. Rev. Lett. 80, 3364 (1998).
25. S. J. Chen, C. F. Chang, H. L. Tsay, and H. D. Yang, J.-Y. Lin Phys. Rev. B 58, R14753 (1998).
26. S. Nishizaki, Y. Maeno and Z. Mao, J. Phys. Soc. Jpn. 69, 573 (2000).
27. H. Won and K. Maki, Europhys. Lett. 54, 248 (2001).
28. H. Won and K. Maki, cond-mat/0004105.
29. H. Won and K. Maki, Europhys. Lett. 56, 729 (2001).
30. C. F. Chang, J.-Y. Lin, H. D. Yang, Phys. Rev. B 61, 14350 (2000).
31. Yu. S. Barash and A. A. Svidzinsky, Phys. Rev. B 53, 15254 (1996); ibid 58, 6476 (1998).
32. C. Kübert and P. J. Hirschfeld, Phys. Rev. Lett. 80, 4963 (1998).
33. I. Vekhter, P. J. Hirschfeld, J. P. Carbotte, E. J. Nicol, Phys. Rev. B 59, R9023 (1999).
34. H. Won and K. Maki, Current Applied Physics 1, 291 (2001); H. Won and K. Maki, in *Vortices in Unconventional Superconductors and Superfluids*, edited by R. P. Huebner, N. Schopohl and G. E. Volovik, Springer (Berlin 2002) pp.243-252.
35. M. B. Salamon, F. Yu and V. N. Kopylov, J. Superconductivity 8, 449 (1995).
36. F. Yu, M. B. Salamon, A. J. Leggett, W. C. Lee, and D. M. Ginsberg Phys. Rev. Lett. 74, 5136 (1995).
37. H. Aubin, K. Behnia, and M. Ribault Phys. Rev. Lett. 78, 2624 (1997).
38. R. Ocaña and P. Esquinazi Phys. Rev. Lett. 87, 167006 (2001).
39. H. Won and K. Maki, Physica B312-313 (2002)
44. *Rare Earth Transition Metal Borocarbides* edited by K.-H. Müller and V. N. Narozhnyi (Kluwer Academic, Dordrecht, 2001), pp. 379-392.
40. M. A. Tanatar, M. Suzuki, S. Nagai, Z. Q. Mao, Y. Maeno, and T. Ishiguro Phys. Rev. Lett. 86, 2649 (2001).
41. H. Won and K. Maki, .
42. K. Izawa, H. Yamaguchi, Y. Matsuda, H. Shishido, R. Settai, and Y. Onuki Phys. Rev. Lett. 87, 057002 (2001).
43. B. Lussier, B. Ellman and L. Taillefer, Phys. Rev. B 53, 5145 (1996).
44. H. Tou, Y. Kitaoka, K. Asayama, N. Kimura, Y. Onuki, E. Yamamoto, and K. Maezawa, Phys. Rev. Lett. 77, 1374 (1996).
45. G. Yang and K. Maki, Europhys. J. B 21 (2001) 61.
46. May Chiao, R. W. Hill, Christian Lupien, and Louis Taillefer P. Lambert and R. Gagnon P. Fournier Phys. Rev. B 62, 3554 (2000).
47. M. Suzuki, M. A. Tanatar, Z. Q. Mao, Y. Maeno, and T. Ishiguro, Phys. Rev. B (in press).
48. M. T. Béal-Monod and K. Maki, Phys. Rev. B 53, 5775 (1996); K. Maki and M. T. Béal-Monod, Phys. Lett. A 208, 365 (1995).

49. C. Petrovic R. Movshovich, M. Jaime, P. G. Pagliuso, M. F. Hundley, J. L. Sarrao, Z. Fisk and J. D. Thompson Europhys. Lett. 53, 354 (2001) and cond-mat/0103168 and J.Phys.Cond.Matt.13 (2001) L337.